

# The use of therapeutic and heat-insulating properties of siliceous gaize in the agricultural sector of the Republic of Kazakhstan

Nurgul Montayeva<sup>1</sup>, Sarsenbek Montayev<sup>2\*</sup>, Ainur Taudaeva<sup>2</sup>, Muratbai Ryskaliev<sup>2</sup>, Sabit Zharylgapov<sup>2</sup>

<sup>1</sup> Institute of Veterinary Medicine and Livestock, Zhangir Khan West Kazakhstan Agrarian-Technical University

<sup>2</sup> Industrial and Technological Institute, Zhangir Khan West Kazakhstan Agrarian-Technical University

## ABSTRACT

The unsatisfactory environmental situation in the regions of Kazakhstan has a significant impact on the health of farm animals, and livestock products are contaminated with heavy metals such as cadmium, lead, and zinc. Taking into account the ecological state of the environment of the regions, it is necessary to introduce sorbents as feed additives that have a positive effect on the health and quality of meat products. In addition, alimentary diseases associated with the use of poor-quality deficient feed and improper organisation of sanitary measures cause significant economic damage to livestock farming. This explains the relevance of this study. The object of this study is the selection of a natural environmentally friendly raw material and its comprehensive use for obtaining a mineral feed additives and heat-insulating ceramic materials suitable for thermal insulation of the enclosing structures of agricultural buildings. To achieve this goal, gaize rocks of the Taskalinsky deposit in the West Kazakhstan Region are of the greatest interest as a natural, environmentally safe raw material. To determine the local elemental composition of the samples, scanning electron microscopy with energy-dispersive microanalysis was performed. Inductively coupled plasma mass spectrometry was carried out to determine the chemical composition, and mineralogical composition was determined using X-ray diffractometry. Experimental analysis of gaize rocks from the Taskalinsky deposit found that the basis of the mineral part is silicon (Si), which is one of the necessary minerals for the animal body. The mineral part of gaize also contains Na, Mg, Ca, K, and Fe, which are also useful for the animal body. The resulting material can be used as a heat-insulating and structural material for the construction of external and internal walls, for the construction of a warm and chemically resistant floor and as a heater for the roof of agricultural buildings and livestock housing.

**Keywords:** Animal husbandry, Livestock and Poultry keeping, Mineral additives, Farm animals, Roof insulation

## Corresponding Author:

Sarsenbek A. Montayev  
Industrial and Technological Institute  
Zhangir Khan West Kazakhstan Agrarian-Technical University  
090009, 51 Zhangir khan Str., Uralsk, Republic of Kazakhstan  
E-mail: smontayev7478@tanu.pro

## 1. Introduction

Agriculture is the main driver of sustainable development of the economy of Kazakhstan. One of the strategic directions is the development of rural areas and state support of farms engaged in animal husbandry. Therefore, at present, the construction of special agricultural buildings and structures to ensure indoor maintenance of animals at the poultry farms has begun to rapidly develop. In these settings, the organism of livestock and poultry is constantly under the influence of a wide variety of environmental factors.

In terms of importance, these factors can be distinguished in the following order:

- 1) ecological environment;
- 2) quality of feed and water;

© The Author 2021. This work is licensed under a [Creative Commons Attribution License](https://creativecommons.org/licenses/by/4.0/) (https://creativecommons.org/licenses/by/4.0/) that allows others to share and adapt the material for any purpose (even commercially), in any medium with an acknowledgement of the work's authorship and initial publication in this journal.



- 3) development of new enclosing structures and materials for buildings that provide comfortable conditions in rooms where animals are kept;
- 4) the pattern of feeding and watering animals;
- 5) a set of sanitary measures to prevent diseases.

The deteriorating environmental situation in the country has a significant impact on the health of farm animals. Due to pollution of soil, water, and plants, livestock products are contaminated with such heavy metals as cadmium, lead and zinc [1; 2; 3; 4]. Taking into account the ecological state of the environment of the regions, it is necessary to introduce sorbents into the feed of livestock and poultry, which will provide a positive effect on the health and quality of meat products. Significant economic damage to livestock is caused by non-infectious, alimentary diseases due to the use of poor-quality, deficient feed and improper organisation of sanitary measures. As a result, the problem of proper feeding of cattle and poultry and keeping them in environmentally friendly buildings constructed from natural raw materials is of particular relevance. It should be noted that these materials must possess high heat-shielding and construction qualities to provide comfort indoors.

Striving for profitability of production in market conditions, livestock and poultry breeders are forced to use more advanced technologies that ensure the maximum level of health and productivity of livestock [5-10]. At the present stage, one of the progressive ways in achieving the set goals is the use of mineral and biologically active substances in animal feeding. Premixes, mineral and vitamin mixtures play a significant role in this. Analysis of data from foreign and Kazakhstani practice shows that their use in feeding livestock has always been effective [11-20]. However, the purchase of premixes, mineral and vitamin mixtures for animal feeding always requires a significant investment of money. Therefore, it seems promising to use natural sorbents as unconventional feed additives. In this regard, the search for effective, easily assimilated mineral feed additives that compensate for the deficiency of microelements in animal body, ensuring disease prevention is of particular relevance. The optimal therapeutic measures are products of mineral and biological origin from the area where the growth and development of the animal takes place.

In recent years, interest in the use of alternative local mineral resources in the general feed balance has increased. Significant positive experimental data have been accumulated on the use of zeolite-containing tuffs of the volcanic and volcanic-sedimentary type (with a zeolite content of 50-60% or more) as a mineral additive in the diets of livestock and poultry [21-28]. The effect of zeolites is manifested primarily in the gastrointestinal tract. It is due to the buffering, ion-exchange, and sorption properties. There are positive results of using siliciferous marls as a mineral supplement for a dairy herd, young cattle, poultry, fur-bearing animals.

In parallel with solving the problem of rational animal feeding, it is necessary to solve the problem of creating comfortable conditions for their keeping. One of the important factors in preserving the health and productivity of animals is the creation of the required microclimate inside the premises where animals are kept. The results of many years of research indicate that the wrong choice of building materials for the construction of external walls and flooring and other structural solutions for agricultural buildings also negatively affects the health and productivity of animals. In such a situation, the temperature and humidity conditions, as well as normal air exchange, are violated inside the room. It has been proven that the ambient air temperature significantly affects the metabolism in the body of animals. Not only the health of animals depends on this, but also their productivity. If the air temperature is low, then the metabolism in the body of animals increases, heat production increases, as a result of which the animals require additional feed. To avoid an increase in feed costs and maintain a favourable microclimate, it is necessary to create an optimal temperature regime in livestock housing. A favourable air temperature is considered to be +10 – +15 °C. For example, if a cow is kept at temperatures below +5 °C, then there is a decrease in milk yield from each cow by 1-2 litres, which leads to an increase in production costs. This means that it is very important to ensure good and high-quality insulation of the barn.

The object of this study is the selection of a natural, ecologically clean raw material and its comprehensive use to obtain a mineral feed additive and heat-insulating ceramic material, suitable for thermal insulation of the enclosing structures of agricultural buildings [29-36].

## 2. Materials and methods

To achieve this goal, the gaize of the West Kazakhstan Region are of the greatest interest as a natural ecologically clean raw material. Gauze mined in the West Kazakhstan is a light, solid, microporous rock

(Figure 1). The siliceous deposit has a colloidal microgranular structure and opal-chalcedony composition. According to geological data, gaize is deposited in Paleogene and Cretaceous sediments and are formed in sea basins due to the compaction and cementation of diatomites and tripoli. Their density is  $1.3-1.5 \text{ g/cm}^3$ . White or gray, greenish light rocks with rare remnants of diatoms, radiolarians, and sponge spicules.



Figure 1. Gaize – siliceous rock of the West Kazakhstan deposit in its natural form

To create a favourable temperature regime in winter, it is necessary to calculate the thermal insulation of buildings. The heat output of cows in the barn at  $+10 \text{ }^{\circ}\text{C}$  should exceed the heat loss of the structure. And since animals need an influx of fresh air, it is necessary to take into account the heat loss caused by the operation of the ventilation system. And if the room is ventilated less often, then the level of ammonia vapours in the air in the barn will increase. The formation of toxic ammonia fumes causes poor health in cows, a decrease in their appetite and productivity. The wrong choice of materials for thermal insulation of walls, floors, and roofs of agricultural buildings for keeping animals leads to the condensate formation on internal surfaces. As a result, the room creates favourable conditions for the reproduction of various pathogenic bacteria. Therefore, there is an objective need for further scientific investigation to improve the composition of feed and create new types of heat-insulating materials to improve the conditions for animal housing [37-42].

When selecting a raw material, it is necessary to consider their versatility. In short, one raw material should serve as a mineral feed additive and a heat-insulating material for the enclosing structures of livestock buildings. As one of the promising ways to solve this problem, it is proposed to use siliceous opal-cristobalite rocks – gaizes and their varieties – gaize-like clays, which are widespread in many regions of Kazakhstan. The use of this type of raw material for the production of heat-insulating ceramic materials is of great interest due to their chemical and mineralogical composition, providing unique properties such as lightness, high porosity, thermal insulation and the ability to sinter during heat treatment [43-55]. The future belongs to ceramic materials with a porous structure (porosity up to 62-68%), with a density of  $700-800 \text{ kg/m}^3$  and increased heat-shielding properties (thermal conductivity less than  $0.2 \text{ W/m}^{\circ}\text{C}$ ). In developed countries, the share of such ceramic materials is up to 50-80% of the total volume of manufactured products [56-67]. Studies of the chemical and mineralogical composition of siliceous rock – the gaize of the Taskalinsky deposit in the West Kazakhstan Region (Figures 2, 3).

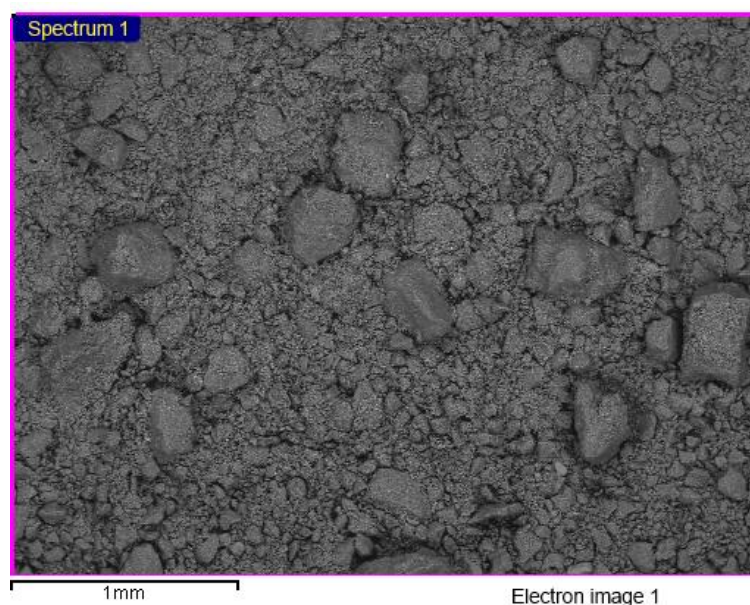


Figure 2. The microstructure of the gaize of the Taskalinsky deposit

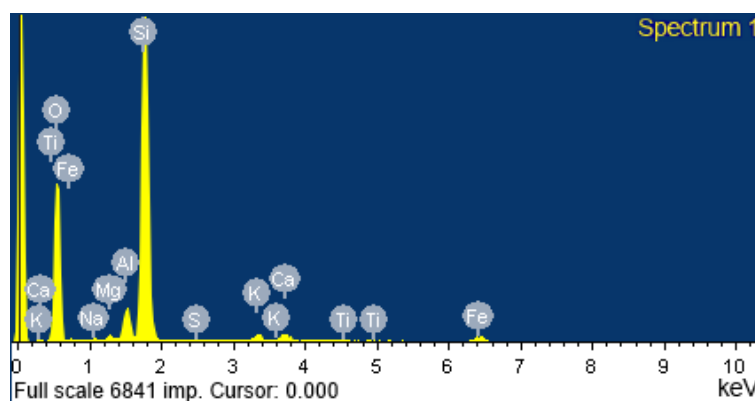


Figure 3. Spectrum of siliceous rock in the gaize of the Taskalinsky deposit

The reserves of gaize are more than 4570 thousand m<sup>3</sup>. The useful stratum is represented by thin-layered porous rock of light grey colour from the Lower Paleogene sediments. The thickness of the useful strata is 4.25-28.0 m, the average is 19.1 m. The study used the following modern analytical equipment of the regional engineering laboratories of Auezov South Kazakhstan State University: scanning electron microscope JSM-6390LV with a system of energy-dispersive microanalysis; X-ray diffractometer X'Pert PRO MPD; inductively coupled plasma mass spectrometer ICP-MS Agilent 7500cx. To determine the local elemental composition of the samples, scanning electron microscopy with energy-dispersive microanalysis was performed. Inductively coupled plasma mass spectrometry was carried out to determine the chemical composition, and mineralogical composition was determined using X-ray diffractometry.

### 3. Results and discussion

One of the common raw materials promising for the use as a mineral component in the creation of biomineral active substances are siliceous-carbonate rocks with high sorption properties and elements useful for the animal body. These siliceous rocks are sedimentary deposits distinguished by the presence of well-preserved remains of flora and fauna, consisting of biogenic silica (radiolaria and diatoms) [68; 75]. In addition, gaizes are capable of forming a ceramic shard with high porosity and low thermal conductivity [76-81]. Therefore, scientific and experimental studies were carried out in two directions: the use of gaize as a mineral feed additive and an adsorbent for birds; the use of gaize as the main raw material for obtaining a porous ceramic material with low thermal conductivity [82-124].

The studies showed that the bulk of the opal mass of the rock is literally "saturated" with clay substance. The clay component is present in the amount of 20-50%. There are individual organogenic remains in the form of sponge spicules. Silty material is represented mainly by quartz grains (up to 15%) and glauconite grains (about 5%) of bright green colour. Relatively large (up to 0.5 mm) mica flakes are quite often observed. The concentration of iron hydroxides is clearly visible along the microcracks. Analysis of the gaize sample made it possible to assert that the sample has an amorphous structure. The spectrum of X-ray diffraction patterns clearly shows the prevalence of quartz –  $\text{SiO}_2$ . Opal is represented by a structureless and microglobular mass, in places it turns into chalcedony. There is an admixture of clay, sandy grains of quartz, feldspars, mica, glauconite (Table 1). The sorption properties of gaizes were determined using the Sorbtometer-M device at the Tambov State Technical University.

Table 1. Chemical elemental composition of the gaize of the Taskalinsky deposit

Element	Weight %	Atomic %
O	53.68	67.97
Na	0.21	0.18
Mg	0.55	0.46
Al	3.40	2.55
Si	36.53	26.35
S	0.19	0.12
K	1.18	0.61
Ca	1.33	0.67
Ti	0.18	0.08
Fe	2.75	1.00

Due to the smallest constituent particles, gaize has a huge adsorption surface. According to the research data, the sorption capacity of the gaize was within 800-850,  $\text{m}^2/\text{g}$ . Natural sorbents as gaize contain a large amount of biogenic macro-, micro-, and ultra-microelements, which can actively participate in a wide variety of metabolic processes and correct the biochemical and antigenic-structural homeostasis of animals.

The first series of experiments was carried out on 320-day old laying hens on the basis of scientific laboratories of the "Shamshyrak" agricultural production cooperative (APC) in the city of Uralsk, West Kazakhstan Region. In the first (experimental) and second (control) groups, the number of birds at the beginning of the experiment was 300. A production test of the effectiveness of the gaize as an adsorbent of toxins was carried out with mixed chronic mycotoxicosis of birds. During mycotoxicological studies of 4 samples of compound feed, molds of the *Fusarium*, *Mucor*, *Aspergillus* genera were isolated. A test on *Stylonychia* showed low toxicity of feed. The following mycotoxins were identified by enzyme-linked immunosorbent assay using ELISA-OEP device: T2 at a concentration of  $93 \pm 5 \mu\text{g}/\text{kg}$  and ochratoxin A at a concentration of  $11 \pm 3 \mu\text{g}/\text{kg}$ .

The average egg production of birds was 71.4%, survival rate was 85.4%. In bacteriological studies of pathological material, pathogens of infectious diseases have not been isolated. The main causes of mortality were non-infectious diseases: hepatitis, enteritis, cloacitis. In a sick bird, clinical signs were manifested by despondency, comb and jowl cyanosis, and refusal to feed. Defecation was impaired, the skin around the cloaca was inflamed, hyperemic, edematous, and contaminated with feces. The experiments were carried out for 90 days. Experimental group of birds No. 1 was fed with the gaize supplement in ten-day cycles with two-stage mixing with fractions of 1-2 mm in a mixture with compound feed in amount of 2% of the mass of feed. Control group No. 2 received feed of the main ration used on the farm. Throughout the experiment, a daily clinical examination of the laying hens was carried out, the productivity and safety were recorded, the feed conversion was assessed, and a postmortem examination of the dead bird was carried out to establish and clarify the diagnosis. The results of the experiment are presented in the Table 2.

Table 2. The efficiency of using gaize as an adsorbent of toxins in poultry farming (M±t; p=10690)

Groups	Animal units	Egg production rate, %	Dead	
			animals	%
Experimental group No. 1	300	86.4%	18*	7.0
Control group No. 2	300	76.5%	33	11.0

Note: \* – degree of confidence  $P < 0.05$

From the data in the table, it can be seen that during the experiment, egg production in the experimental group increased by 9.9%. The difference in mortality between the groups was 4.0%. In addition, the average weight of one egg of the hens in the experimental group by the end of the experiment was 3.8 g more (51.7 g versus 47.9 g in the control).

In the course of the study, it was found that the inclusion of an adsorbent in the form of gaize in the diets of laying hens leads to an increase in the quality of the shell and an increase in the mass of eggs. It should be noted that feeding the adsorbent, the active component of which is gaize, enhances the sorption of calcium from the feed due to an excess negative charge on the surface of the latter, followed by re-adsorption of this macroelement in the gastrointestinal tract, which, in turn, leads to an improvement in the quality of the shell, reduction of notches and breakage.

In the experimental group, the eggs obtained from the hens were distinguished by their greater strength. Thus, gaize, used as an active base of the adsorbent, due to the peculiarities of its crystal structure, has a high sorption activity, which allows it to effectively bind and remove toxic substances from the body, and first of all, toxins of microbial cells and mycotoxins. Largely due to all of the above properties of the gaize, the use as an adsorbing agent when feeding mixed fodder affected by mould fungi and their metabolites, in doses from 0.5 to 2% of diet in dry matter, relieves symptoms of toxicosis. In addition, it has a positive effect on the physiological state, safety and productivity of animals, and also improves feed intake.

To carry out experimental efforts in the other direction, the gaize was first dried in a drying cabinet and subjected to preliminary crushing using a laboratory jaw crusher. Then gaize was ground in a laboratory ball mill until it passed through No. 1.0. The composition of the raw mixture was selected with the following limiting concentrations of components, wt.%: gaize 70-80, clay 17-25, coal 3-5 (Table 3).

Table 3. The studied compositions of ceramic masses based on gaize

No. of composition	Name and content of raw materials, wt.%		
	gaize	clay	coal
1	70	25	5
2	75	21	4
3	80	17	3

By weighing, the raw materials were dosed according to the test compositions and loaded into a laboratory ball mill for joint grinding to obtain a homogeneous powder mixture. The resulting mixture was fed into a laboratory mixer and water was added and thoroughly mixed again until a plastic ceramic mass was obtained. The moulding moisture content of the ceramic mass was 25-27% by weight of dry components. Samples of cylinders with dimensions of 50x50x50 mm were moulded from the ceramic mass by the soft-mud process. The resulting cylinder samples were dried in a drying oven to a residual moisture content of 8-10%. General appearance of raw cylindrical samples is shown in the Figure 4.





Figure 4. Laboratory raw cylindrical samples

The obtained cylindrical samples were fired at a temperature of 1000 °C in a laboratory muffle furnace with a temperature elevation rate of 150 °C per hour. The samples were soaked at the final temperature for 1 hour, and then left with the oven turned off to room temperature. Heat-treated ceramic cylindrical samples were subjected to physical and mechanical tests according to the rules of standard procedures. The most important physical and mechanical properties of the sample were chosen as the studied properties, characterising their efficiency as average density, g/cm<sup>3</sup>, compression resistance, MPa, water absorption, %, total porosity, %, thermal conductivity, W/(m°C), and chemical resistance to 10% hydrochloric acid (HCl). General appearance of heat-treated cylindrical samples at a firing temperature of 1000 °C is presented in the Figure 5.

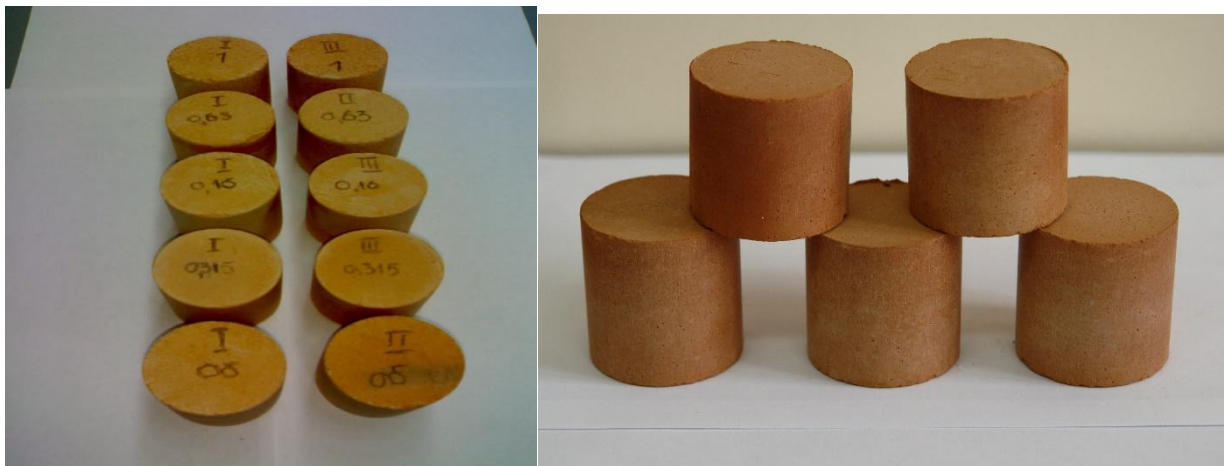


Figure 5. Laboratory cylindrical samples heat-treated at a temperature of 1000 °C

For a comparative analysis of the results of experimental work, control samples based on ceramic masses of pure loam were moulded in parallel. The results are presented in the Table 4.

Table 4. Physical and mechanical properties of ceramic samples heat-treated at a temperature of 1000 °C

No. of composition	Average density, g/cm <sup>3</sup>	Compressive resistance, MPa	Water absorption, %	Total porosity, %	Thermal conductivity, W/(m°C)	Chemical resistance to 10% HCl
1	0.62	12.4	33	57	0.21	96.3
2	0.67	11.9	32	54	0.23	97.5
3	0.71	10.7	31	52	0.27	98.4
Loam control samples	1.85	7.5	25	22	0.7	80.4

As a result of the analysis of the physical and mechanical properties of heat-treated samples at temperatures of 1000 °C, it was possible to establish the basic laws of their change depending on the component composition of the raw material system. Comparative analysis of changes in the physical and mechanical properties of samples of the studied compositions of ceramic masses in comparison with ceramic samples based on loam showed significant changes in all properties. Specimens based on the investigated ceramic mass have a lower average density, higher chemical resistance, and total porosity increased more than 2 times. In addition, they have a reduced coefficient of thermal conductivity (0.21-0.27 W/m°C versus 0.7-0.8 W/m°C), which is one of the important criteria for the energy efficiency of the material. In addition, despite the high values of total porosity, the samples have high compressive strength (10.7-12.4 MPa versus 7.05 MPa).

To study the morphology of the porous structure of the studied ceramic cylinders, the samples were cut using a cutting tool (Figure 6). On the basis of visual inspection and examination under a microscope, it can be stated that the samples are a strongly sintered ceramic material of light red colour with a macro- and microporous structure. Macro- and micropores are evenly distributed throughout the volume.



Figure 6. The porous macrostructure (in the cut) of heat-treated cylindrical samples at a temperature 1000°C

The changes occurring in the physical and mechanical properties in the studied ceramic masses are associated, first of all, with the chemical and mineralogical characteristics of the raw materials used. A decisive role in the establishment of a porous structure and low average density and thermal conductivity is played by siliceous rock – gaize and coal. By nature, it has high porosity and low average density. Clay acts as a binder for two non-plastic materials in the shaping stages and the solid-phase and liquid-phase sintering at the firing stage. As a result, a sintered solid crystalline phase with a fine-pored structure is formed, which explains the high strength characteristics of the samples, despite the high total porosity. Thus, on the basis of the investigated compositions of ceramic masses, it is possible to obtain effective ceramic materials differing in lightness, required strength, high chemical resistance, high total porosity, and low values of the thermal conductivity coefficient.

The results of studies of the second direction show that the obtained material can be used as a heat-insulating and structural material for the construction of external and internal walls, a warm and chemically resistant floor and as a heater for the roof of agricultural buildings and livestock housing. The considered material meets the number of important criteria:

- fire safety, as the ceramic material based on the gaize is not combustible;
- ecological safety, since the composition of material is completely free of substances that can harm the health of animals;
- vapour resistance, which prevents condensation that can worsen indoor climate and cause active rotting of feed and bedding;
- eliminates the destructive effect of condensation on the structure of an agricultural building;
- mechanical strength, in case of accidental impacts the material does not collapse or fracture;
- chemical resistance of the material excludes decay of the building from the effects of chemical factors.



#### 4. Conclusion

Based on the findings of scientific, experimental, and empirical research, the most important factors affecting the health and productivity of animals and birds have been identified. In terms of influence, these factors can be distinguished in the following order:

- 1) ecological environment;
- 2) quality of feed and water;
- 3) development of new enclosing structures and materials for buildings that provide comfortable conditions in rooms where animals are kept;
- 4) the pattern of feeding and watering animals;
- 5) a set of sanitary measures to prevent diseases.

The studies of chemical and mineralogical composition, the structural and biological characteristics of gaize of the Taskalinsky deposit revealed the following special properties:

- the basis of the mineral part of gaize is silicon (Si), which is one of the essential minerals for the animal organism;
- the composition of the mineral part of the gaize also contains Na, Mg, Ca, K, Fe, which are also useful for animals;
- high sorption capacity of the considered mineral predetermines the possibility of its use as a sorbent for cleaning the animal body from toxins;
- physical and mechanical properties of gaize provide the creation of effective heat-insulating ceramic materials that are lightweight, durable, with high chemical resistance, porous structure, and low heat conductivity.

The study shows that the obtained material can be used as a heat-insulating and structural material for the construction of external and internal walls, a warm and chemically resistant floor, and as a heater for the roof of agricultural buildings and livestock housing.

#### References

- [1] Z. Iqbal, F. Abbas, M. Ibrahim, T. I. Qureshi, M. Gul, and A. Mahmood, "Human Health Risk Assessment of Heavy Metals in Raw Milk of Buffalo Feeding at Wastewater-Irrigated Agricultural Farms in Pakistan," *Environmental Science and Pollution Research*, vol. 27, no. 23, pp. 29567-29579, 2020.
- [2] R. B. Temiraev, V. R. Kairov, E. S. Dzodzieva, N. A. Erenee, R. Z. Abdulkhalikov, and I. M. Kulova, "Quality Control of Pork When Feeding Enzyme Preparations and Adsorbents," *Meat Industry*, vol. 3, pp. 43-46, 2016.
- [3] K. F. Johnson, N. Chancellor, C. C. Burn, and D. C. Wathes, "Analysis of Pre-Weaning Feeding Policies and Other Risk Factors Influencing Growth Rates in Calves On 11 Commercial Dairy Farms," *Animal*, vol. 12, no. 7, pp. 1413-1423, 2018.
- [4] M. P. Kirilov, "New Generation of Biologically Active Substances in Animal Feeding," *Feeding of Farm Animals and Fodder Production*, vol. 3, pp. 34-37, 2006.
- [5] E. V. Ulrikh, R. S. Khaliullin, I. A. Ganieva, E. A. Izhmulkina, and M. N. Arzjutov, "The Content of Biologically Active Substances in Phytobiotics used for Agricultural Animals and Poultry," *International Journal of Engineering and Technology (UAE)*, vol. 7, no. 3.14 Special Issue 14, pp. 445-449, 2018.
- [6] S. I. Kononenko, E. N. Golovko, N. N. Zabashta, and A. Z. Utizhev, "Correction of Rations for Pigs Reared for The Production of Organic Pork," *Bulletin of Agrarian Science of the Don*, vol. 2, no. 34, pp. 49-58, 2016.
- [7] G. C. Shurson, "Yeast and Yeast Derivatives in Feed Additives and Ingredients: Sources, Characteristics, Animal Responses, and Quantification Methods," *Animal Feed Science and Technology*, vol. 235, pp. 60-76, 2018.

- 
- [8] W. Górniak, P. Cholewińska, and D. Konkol, "Feed Additives Produced on The Basis of Organic Forms of Micronutrients as A Means of Biofortification of Food of Animal Origin," *Journal of Chemistry*, vol. 2018, Article number 8084127, 2018.
  - [9] O. A. Bagno, O. N. Prokhorov, S. A. Shevchenko, A. I. Shevchenko, and T. V. Dyadichkina, "Use of Phytobiotics in Farm Animal Feeding," *Sel'Skokhozyaistvennaya Biologiya*, vol. 53, no. 4, pp. 687-697, 2018.
  - [10] E. Pecka-Kielb, A. Zachwieja, E. Wojtas, and W. Zawadzki, "Influence of Nutrition on The Quality of Colostrum and Milk of Ruminants," *Mljekarstvo*, vol. 68, no. 3, pp. 169-181, 2018.
  - [11] V. D. Kotlyar, and K. A. Lapunova, "Technological Features of Gaizes as Raw Materials for Wall Ceramics," *Proceedings of Universities. Construction*, vol. 11-12, pp. 25-31, 2009.
  - [12] V. D. Kotlyar, B. V. Talpa, and Yu. V. Terekhin, "Evaluation of Siliceous Opoka-Like Rocks for The Production of Ceramic Bricks," *Building Materials*, vol. 12, pp. 20-22, 2010.
  - [13] V. D. Kotlyar, "Features of Pressing Ceramic Powders Based on Gaizes in The Production of Wall Ceramics," *Construction Materials*, vol. 12, pp. 28-32, 2009.
  - [14] S. A. Montaev, and N. S. Montaeva, "The Technology for The Production of Artificial Crushed Stone from Siliceous Rock – Gaize," *Bulletin of the National Engineering Academy of the Republic of Kazakhstan*, vol. 2, pp. 86-92, 2014.
  - [15] G. D. Ashmarin, V. G. Lastochkin, V. V. Ilyukhin, A. G. Minakov, and A. B. Tatyanchikov, "Innovative Technologies of Highly Efficient Ceramic Building Products Based on Siliceous Rocks," *Building Materials*, vol. 7, pp. 28-30, 2011.
  - [16] K. S. Dmitriev, "Porous Ceramics: Current State and Prospects," *International Journal of Experimental Education*, vol. 7, pp. 152-154, 2016.
  - [17] V. F. Zavadsky, N. B. Putro, and Yu. S. Maksimova, "Porous Building Ceramics," *Building Materials*, vol. 2, pp. 21-18, 2004.
  - [18] M. G. Gabidullin, R. A. Kagomov, R. Z. Rakhimov, and A. V. Temlyakov, "Relationship Between the Structure and Thermophysical Properties of Porous Ceramics," *Building Materials*, vol. 9, pp. 62-65, 2005.
  - [19] V. D. Kotlyar, B. V. Talpa, and Yu. V. Terekhina, "Evaluation of Siliceous Opoka-Like Rocks for The Production of Ceramic Bricks," *Construction Materials*, vol. 12, pp. 20-22, 2010.
  - [20] S. A. Mizuriaev, S. A. Montaev, and A. T. Taskaliev, "Artificial Broken Stone Production for Industrial and Civil Engineering: Technological Parameters," *Procedia Engineering*, vol. 111, pp. 534-539, 2015.
  - [21] V. S. Pashtetsky, V. V. Khomenko, N. P. Demchenko, N. Y. Poliakova, and R. V. Kashbrasiev, "Sustainable and Competitive Agricultural Development of a Water-Deficient Region (Case of the Crimean Peninsula)," *Geography, Environment, Sustainability*, vol. 13, no. 2, pp. 65-72, 2020.
  - [22] E. Barbotkina, I.E. Dunaieva, V. Popovych, and V. Pashtetsky, "Review of Methods and Approaches of Abandoned Lands Identification," *E3S Web of Conferences*, vol. 224, article number 04004, 2020.
  - [23] R. Beisenova, Z. Rakhymzhan, R. Tazitdinova, A. Auyelbekova, and M. Khussainov, "Comparative Characteristics of Germination of Some Halophyte Plants in Saline Soils of Pavlodar Region," *Journal of Environmental Management and Tourism*, vol. 11, no. 5, pp. 1132-1142, 2020.
  - [24] L. Akbayeva, N. Mamytova, R. Beisenova, R. Tazitdinova, A. Abzhalelov, and A. Akhayeva, "Studying the Self-Cleaning Ability of Water Bodies and Watercounts of Arshalyn District of Akmola Region," *Journal of Environmental Management and Tourism*, vol. 11, no. 5, pp. 1095-1104, 2020.
  - [25] R. Baizholova, Z. Abylkassimova, and A. Ramashova, "Problems of Staffing for Innovation Sector," *Actual Problems of Economics*, vol. 178, no. 4, pp. 232-245, 2016.
-

- 
- [26] S. Shamsledenova, R. Beisenova, Z. Rakhymzhan, Z. Zhaznaeva, N. Syzdykova, R. Tazitdinova, and M. Khanturin, "Ecological Characteristics of Groundwater in Rural Areas of The Karaganda Region," *Journal of Ecological Engineering*, vol. 20, no. 11, pp. 67-75, 2019.
  - [27] I. Sultangaliyeva, R. Beisenova, R. Tazitdinova, A. Abzhalelov, and M. Khanturin, "The Influence of Electromagnetic Radiation of Cell Phones on The Behavior of Animals," *Veterinary World*, vol. 13, no. 3, pp. 549-555, 2020.
  - [28] R. Beisenova, S. Tulegenova, R. Tazitdinova, O. Kovalenko, and G. Turlybekova, "Purification by Ketoconazole Adsorption from Sewage," *Systematic Reviews in Pharmacy*, vol. 11, no. 6, pp. 550-554, 2020.
  - [29] G. Chen, Z. Jiang, and M. M. Kamruzzaman, "Radar Remote Sensing Image Retrieval Algorithm Based on Improved Sobel Operator," *Journal of Visual Communication and Image Representation*, vol. 71, article number 102720, 2020.
  - [30] A. Zholdasbekova, K. B. Biyashev, B. K. Biyashev, D. A. Sarybaeva, and K. T. Zhumanov, "Method for Producing Attenuated Salmonella Strain," *Journal of Pharmaceutical Sciences and Research*, vol. 10, no. 1, pp. 162-163, 2018.
  - [31] K. T. Zhumanov, K. B. Biyashev, B. K. Biyashev, A. R. Sansyzbai, and A. Valdovska, "Application of Polyvalent Hyperimmune Serum Against Mastitis in Beef Cattle," *Biology and Medicine*, vol. 7, no. 5, article number BM-154-15, 2015.
  - [32] A. Shoman, A. Serikbayeva, L. Mamayeva, B. Faye, and T. Tultabayeva, "A Biological Analysis of Endocrine-Disturbing Chemicals in Camel Meat Sector in Kazakhstan," *EurAsian Journal of BioSciences*, vol. 12, no. 2, pp. 473-479, 2018.
  - [33] E. Nagyzbekkyzy, G. Abitayeva, S. Anuarbekova, D. Shaikhina, K. Li, S. Shaikhin, K. Almagambetov, A. Abzhalelov, S. Saduakhassova, A. Kushugulova, and F. Marotta, "Investigation of Acid and Bile Tolerance, Antimicrobial Activity and Antibiotic Resistance of Lactobacillus Strains Isolated from Kazakh Dairy Foods," *Asian Journal of Applied Sciences*, vol. 9, no. 4, pp. 143-158, 2016.
  - [34] K. B. Biyashev, Z. S. Kirkimbaeva, B. K. Biyashev, A. Z. Makbuz, and M. D. Bulegenova, "Determination of The Level of Resistance of Probiotic Strain Escherichia Coli 64g To Hydrochloric Acid, Bile and Antimicrobial Agents," *Ecology, Environment and Conservation*, vol. 25, no. 4, pp. 1930-1933, 2019.
  - [35] R. S. Zhussupov, R. A. Baizholova, I. N. Dubina, and G. T. Sadykova, "Methodology for Assessing the Competitive Advantages of Agriculture in The Northern Regions of Kazakhstan," *Espacios*, vol. 39, no. 16, pp. 1-10, 2018.
  - [36] R. Tazitdinova, R. Beisenova, G. Saspugayeva, B. Aubakirova, Z. Nurgalieva, A. Zandybai, I. Fakhrudanova, and A. Kurmanbayeva, "Changes in The Biochemical Parameters of Rat Blood Under the Combined Effect of Chronic Intoxication with Such Heavy Metals as Copper, Zinc, Arsenic," *Advances in Animal and Veterinary Sciences*, vol. 6, no. 11, pp. 492-498, 2018.
  - [37] N. Aralbayev, F. Dikhanbayeva, A. Serikbayeva, Y. A. Yusof, and Y. N. Abdul Manaf, "Comparative Study of Amino Acid Composition of Raw and Dry Camel Milk and Shubat (Camelus Dromedaries)," *EurAsian Journal of BioSciences*, vol. 13, no. 2, pp. 1489-1493, 2019.
  - [38] D. A. Saribayeva, K. B. Biyashev, A. Valdovska, A. R. Sansyzbai, and B. K. Biyashev, "Study Antagonistic Activity, The Level of Resistance to Hydrochloric Acid and Bile Probiotic Strain Escherichia Coli," *Journal of Pure and Applied Microbiology*, vol. 9, no. 1, pp. 573-578, 2015.
  - [39] L. Metelytsia, D. Hodyna, I. Dobrodub, I. Semenyuta, M. Zavhorodnii, V. Blagodatny, V. Kovalishyn, and O. Brazhko, "Design Of (Quinolin-4-Ylthio) Carboxylic Acids as New Escherichia Coli DNA Gyrase B Inhibitors: Machine Learning Studies, Molecular Docking, Synthesis and Biological Testing," *Computational Biology and Chemistry*, vol. 85, article number 107224, 2020.
-

- 
- [40] S. Shaikhin, A. Sobkiewicz, J. Barciszewski, and T. Twardowski, "Evidence for Plant Ribosomal 5S RNA Involvement in Elongation of Polypeptide Chain Biosynthesis," *Acta biochimica Polonica*, vol. 41, no. 1, pp. 57-62, 1994.
  - [41] K. B. Biyashev, B. K. Biyashev, and A. Z. Makbuz, "Prevalence of Causative Agents of Emergent Food Zoonotic Diseases in Animals, Animal Origin Products and Environmental Objects," *Biology and Medicine*, vol. 8, no. 2, article number BM-169-16, 2016.
  - [42] A. A. Zhakupova, A. Z. Maulanov, B. K. Biyashev, K. B. Biyashev, and N. B. Sarsembaeva, "Histological Study of The Interaction of The Escherichia with Epithelium of The Small Intestine of Rats," *Advances in Environmental Biology*, vol. 8, no. 10, pp. 553-555, 2014.
  - [43] A. Issimov, D. B. Taylor, K. Zhugunissov, L. Kutumbetov, A. Zhanabayev, N. Kazhgaliyev, A. Akhmetaliyeva, B. Nurgaliyev, M. Shalmenov, G. Absatirov, L. Dushayeva, and P. J. White, "The Combined Effects of Temperature and Relative Humidity Parameters on The Reproduction of Stomoxys Species in A Laboratory Setting," *PLoS ONE*, vol. 15, no. 12 December, article number e0242794, 2021.
  - [44] A. A. Zhakupova, K. B. Biyashev, B. K. Biyashev, S. E. Ermagambetova, and G. M. Nurgozhayeva, "Performance Test of The Drug Enterocol," *Journal of Pharmaceutical Sciences and Research*, vol. 9, no. 10, pp. 1941-1942, 2017.
  - [45] M. Bulegenova, K. Biyashev, Z. Kirkimbaeva, B. Biyashev, S. Ermagambetova, K. Oryntayev, and A. Altenov, "The Effect of The Drug Enterocol on The Humoral Factors of Calf Body Resistance," *Advances in Animal and Veterinary Sciences*, vol. 7, no. 8, pp. 674-680, 2019.
  - [46] Z. Sarmurzina, G. Bissenova, K. Zakarya, R. Dospaeva, S. Shaikhin, and A. Abzhalelov, "Characterization of Probiotic Strains of Lactobacillus Candidates for Development of Synbiotic Product for Kazakh Population," *Journal of Pure and Applied Microbiology*, vol. 11, no. 1, pp. 151-161, 2017.
  - [47] A. B. Tastulekova, R. K. Satova, and U. Zh. Shalbolova, "Business Valuation and Equity Management When Entering the IPO Market," *European Research Studies Journal*, vol. 21, no. 4, pp. 875-886, 2018.
  - [48] A. O. Zhupysheva, S. B. Makysh, R. R. Beisenova, L. Z. Beisenova, and R. M. Tazitdinova, "Criteria for Auditing the Efficiency of Natural Resource Use. Example Of the Karaganda Region," *Journal of Environmental Management and Tourism*, vol. 10, no. 7, pp. 1466-1477, 2019.
  - [49] O. Sobol, V. Domatskiy, Y. Koneva, K. Nifontov, and M. Savvinova, "Review of Basic Trends in Cryotherapy Applications for Horse Injuries," *Arquivo Brasileiro de Medicina Veterinaria e Zootecnia*, vol. 72, no. 3, pp. 688-694, 2020.
  - [50] Z. Tulemisova, K. Biyashev, B. Biyashev, G. Kasenova, Z. Kozhakhmetova, and D. Sarybaeva, "Prophylaxy of Gasstro-Intestinal Diseases of Young Animals" *Journal of Animal and Veterinary Advances*, vol. 12, no. 22, pp. 1645-1650, 2013.
  - [51] M. D. Bulegenova, K. B. Biyashev, B. K. Biyashev, Z. S. Kirkimbayeva, and S. E. Ermagambetova, "The Prevalence of Pathogens of Intestinal Zoonoses in Animals and In Environmental Objects," *Journal of Pharmaceutical Sciences and Research*, vol. 10, no. 9, pp. 2373-2375, 2018.
  - [52] A. A. Glukhov, and V. A. Sergeev, "Results of Operative Therapy of Diabetic Foot Purulent Complications Using Programmed Sanitation Technologies," *Zeitschrift fur Gefassmedizin*, vol. 17, no. 3, pp. 13-17, 2020.
  - [53] A. A. Gluxov, and V. A. Sergeev, "Assessment of Efficiency of The Programmed Aspiration and Irrigation Rehabilitation Method in Suppurative Necrotic Complications of Diabetic Foot Syndrome," *Novosti Khirurgii*, vol. 26, no. 3, pp. 311-320, 2018.
  - [54] S. A. Montayev, N. S. Montayeva, A. B. Shinguzhiyeva, K. Zhanabaevichdosov, and M. Zhanaidarovichrskaliyev, "Possibility of Producing Sintered Fine Porous Granulated Ceramic Filler Using Ash of Thermal Power Stations in Combination with Clay Rocks," *International Journal of*
-

*Mechanical and Production Engineering Research and Development*, vol. 9, no. 4, pp. 1087-1096, 2019.

- [55] A. A. Glukhov, V. A. Sergeev, and G. A. Semyonova, "Assessment of the Outcomes of the Treatment of Patients with Suppurative Necrotic Complications of Diabetic Foot Syndrome with the use of Programmed Rehabilitation Technologies," *Grekov's Bulletin of Surgery*, vol. 177, no. 6, pp. 63-68, 2018.
- [56] G. F. Parisi, S. Cutello, G. Di Dio, N. Rotolo, M. La Rosa, and S. Leonardi, "Phenotypic Expression of the p.Leu1077Pro CFTR Mutation in Sicilian Cystic Fibrosis Patients," *BMC Research Notes*, vol. 6, no. 1, pp. 461, 2013.
- [57] B.S. Omirbayeva, R.A. Baizholova, D.M. Nurkhaliyeva, "Health Care System in Transition: Some Aspects of Financing," *Journal of Advanced Research in Law and Economics*, vol. 8, no. 4, pp. 1260-1275, 2017.
- [58] M. Chen, X. Han, H. Zhang, G. Lin, and M. M. Kamruzzaman, "Quality-Guided Key Frames Selection from Video Stream Based on Object Detection," *Journal of Visual Communication and Image Representation*, vol. 65, article number 102678, 2019.
- [59] K. B. Biyashev, B. K. Biyashev, and D. A. Saribayeva, "Persistence of the Escherichia coli 64G-Probiotic Strain in the Intestine of Calves," *Biology and Medicine*, vol. 8, no. 2, pp. 2-3, 2016.
- [60] O. Hrechanina, G. Isayeva, O. Kolesnikova, and Y. Isakova, "Relations Between Familial Hypercholesterolemia and Early Ischemic Heart Disease: An Analysis of Medical Documentation Data," *Serbian Journal of Experimental and Clinical Research*, vol. 21, no. 4, pp. 343-349, 2020.
- [61] G. S. Isayeva, A. V. Martynenko, O. A. Beloded, T. A. Struk, M. V. Vovchenko, and T. N. Bondar, "Effect of Age, Sex Hormones and Aldosterone on SCORE in Perimenopausal Women," *Life Science Journal*, vol. 12, no. 1, pp. 44-49, 2015.
- [62] E. Sidorova, "The Main Factors and Conditions Determining the Feasibility of Production of High-Tech Products Based on The Potential of Applied Research Organizations," *International Multidisciplinary Scientific GeoConference Surveying Geology and Mining Ecology Management, SGEM*, vol. 19, no. 5, pp. 841-847, 2019.
- [63] S. A. Montaeve, N. B. Adilova, N. S. Montaeve, K. Z. Dosov, and A. A. Taudaeva, "Study of Raw Materials with The Aim of Obtaining Ceramic Filler and Heat-Insulating and Structural Wall Ceramics," *International Journal of Mechanical and Production Engineering Research and Development*, vol. 9, no. 5, pp. 1057-1064, 2019.
- [64] A. V. Zhaglovskaya, D. Yu. Savon, A. E. Safronov, and E. Yu. Sidorova, "Production Activity Analysis Methodology for Open Pit Coal Mines (In Terms of Shestaki Open Pit Mine)," *Eurasian Mining*, vol. 2017, no. 1, pp. 14-16, 2017.
- [65] A. Markovska, and A. Isaeva, "Public Sector Corruption: Lessons to Be Learned from The Ukrainian Experience," *Crime Prevention and Community Safety*, vol. 9, no. 2, pp. 118-129, 2007.
- [66] Z. M. Orynkanova, R. A. Baizholova, and A. Z. Zeinullina, "Improving the Energy Efficiency of Kazakhstan's Economy," *Journal of Environmental Management and Tourism*, vol. 11, no. 1, pp. 44-53, 2020.
- [67] I. D. Bobruskin, S. M. Shaikhin, M. V. Muratova, L. A. Baranova, and E. S. Severin, "Allosteric Regulation of Ca<sup>2+</sup>-Calmodulin-Dependent Phosphodiesterase Activity from the Bovine Brain," *Biokhimiya*, vol. 52, no. 8, pp. 1344-1352, 1987.
- [68] A. Issimov, D. B. Taylor, M. Shalmenov, B. Nurgaliyev, I. Zhubantayev, N. Abekeshev, K. Kushaliyev, A. Kereyev, L. Kutumbetov, A. Zhanabayev, Y. Zhakiyanova, and P. J. White, "Retention of Lumpy Skin Disease Virus in Stomoxys SPP (Stomoxys Calcitrans, Stomoxys Sitiens, Stomoxys Indica) Following Intrathoracic Inoculation," *Diptera: Muscidae. PLoS ONE*, vol. 16, no. 2, article number e0238210, 2021.



- 
- [69] E. Y. Sidorova, Y. Kostyukhin, and V. Shtanskiy, "Creation of Conditions for The Development of Production of Science-Intensive Products Based on The Potential of Russian Applied Scientific Organizations," *Smart Innovation, Systems and Technologies*, vol. 139, pp. 584-591, 2019.
  - [70] A. B. Abzhaliyeva, K. B. Biyashev, B. K. Biyashev, D. M. Orazaliev, M. R. Turabekov, and A. A. Taipova, "Prevalence of Intestinal Pathogens in Animals, Food Products of Animal Origin and In the Environmental Objects," *Journal of Pharmaceutical Sciences and Research*, vol. 10, no. 2, pp. 246-247, 2018.
  - [71] O. V. Chernets, V. M. Korzhyk, G. S. Marynsky, S. V. Petrov, and V. A. Zhovtyansky, "Electric Arc Steam Plasma Conversion of Medicine Waste and Carbon Containing Materials," *GD 2008 - 17th International Conference on Gas Discharges and Their Applications*, vol. 1, pp. 465-468, 2008.
  - [72] G. Raiymbek, B. Faye, I. T. Kadim, A. Serikbaeva, and G. Konuspayeva, "Comparative Fatty Acids Composition and Cholesterol Content in Bactrian (*Camelus Bactrianus*) and Dromedary Camel (*Camelus Dromedarius*) Meat," *Tropical Animal Health and Production*, vol. 51, no. 7, pp. 2025-2035, 2019.
  - [73] N. S. Salikova, Z. O. Tleuova, A. S. Kurmanbayeva, R. K. Khussainova, and A. A. Kakabayev, "Distribution of Radionuclides in Natural Waters of Northern Kazakhstan and Assessment of Waterborne Doses Irradiation of Population," *Periodico Tche Quimica*, vol. 17, no. 36, pp. 1016-1037, 2020.
  - [74] V. D. Nazarova, N. S. Salikova, A. U. Bektemissova, B. E. Begenova, and G. B. Aubakirova, "Isolation of Miricetine-Containing Fractions from *Linossyris Villosa* Plant and Their Application as Antianemic Agent," *Periodico Tche Quimica*, vol. 17, no. 35, pp. 998-1012, 2020.
  - [75] M. Yu. Kharlamov, I. V. Krivtsun, and V. N. Korzhyk, "Dynamic Model of The Wire Dispersion Process in Plasma-Arc Spraying," *Journal of Thermal Spray Technology*, vol. 23, no. 3, pp. 420-430, 2014.
  - [76] L. M. Gaisina, M. L. Belonozhko, N. A. Tkacheva, N. K. Abdrakhmanov, and N. V. Grogulenko, "Principles and Methods of Synergy Modeling of Management System at Oil and Gas Sector's Enterprises," *Espacios*, vol. 38, no. 33, pp. 1-5, 2017.
  - [77] A. Zh. Zhusupbekov, A. S. Montayeva, S. A. Montayev, and N. S. Montayeva, "Ensuring Chemical Resistance of Pile Foundations When They Are Installed in Permanently and Seasonally Frozen Soils with Aggressive Environments," *IOP Conference Series: Materials Science and Engineering*, vol. 775, no. 1, article number 012130, 2020.
  - [78] I. Cherunova, S. Tashpulatov, and A. Merkulova, "Development of Automation Algorithm for Step of Designing Technology of Static Electricity Protection Clothing," *2018 International Russian Automation Conference, RusAutoCon 2018*, vol. 1, article number 8501821, 2018.
  - [79] S. A. Montayev, A. S. Montayeva, N. B. Adilova, A. B. Shinguzhiyeva, N. S. Montayeva, and A. T. Taskaliyev, "Prospects of Creating the Technology of Composite Adsorbent for Water Purification Based on The Composition of Siliceous and Clay Rocks of Kazakhstan," *International Journal of Mechanical Engineering and Technology*, vol. 9, no. 1, pp. 805-813, 2018.
  - [80] N. S. Salikova, A. U. Bektemissova, V. D. Nazarova, B. E. Begenova, and N. V. Ostafeichuk, "Preparation of Mixed Hydrogels Based on Biopolymers and The Study of Their Rheological Properties," *Periodico Tche Quimica*, vol. 17, no. 35, pp. 23-40, 2020.
  - [81] Yu. S. Borisov, V. E. Olikier, E. A. Astakhov, V. N. Korzhik, and Yu. A. Kunitskii, "Structure and Properties of Gas-Thermal Coatings of Fe-B-C and Fe-Ti-B-C Alloys," *Soviet Powder Metallurgy and Metal Ceramics*, vol. 26, no. 4, pp. 313-318, 1987.
  - [82] V. A. Pogodin, L. N. Rabinskii, and S. A. Sitnikov, "3D Printing of Components for the Gas-Discharge Chamber of Electric Rocket Engines," *Russian Engineering Research*, vol. 39, no. 9, pp. 797-799, 2019.
-

- 
- [83] V. S. Terent'eva, A. N. Astapov, and L. N. Rabinskiy, "State in the Field of Heat-Resistant Coatings for Heat-Proof Nickel Alloys and Steels," *Periodico Tche Quimica*, vol. 16, no. 33, pp. 561-572, 2019.
  - [84] B. H. Baymuratov, S. S. Tashpulatov, R. D. Akbarov, M. Ilhamova, G. A. Yusuphodkaeva, U. T. Uzakov, and N. A. Yusuphodkaeva, "Development of Special Fabrics Protecting from Electromagnetic Radiation," *IOP Conference Series: Materials Science and Engineering*, vol. 459, no. 1, article number 012031, 2018.
  - [85] G. F. Parisi, S. Leonardi, G. Ciprandi, A. Corsico, A. Licari, M. Miraglia del Giudice, D. Peroni, C. Salpietro, and G. L. Marseglia, "Antihistamines in Children and Adolescents: A Practical Update," *Allergologia et Immunopathologia*, vol. 48, no. 6, pp. 753-762, 2020.
  - [86] M. Y. Kharlamov, I. V. Krivtsun, V. N. Korzhyk, Y. V. Ryabovolyk, and O. I. Demyanov, "Simulation of Motion, Heating, and Breakup of Molten Metal Droplets in The Plasma Jet at Plasma-Arc Spraying," *Journal of Thermal Spray Technology*, vol. 24, no. 4, pp. 659-670, 2015.
  - [87] A. Z. Skorokhod, I. S. Sviridova, and V. N. Korzhik, "Structural and Mechanical Properties of Polyethylene Terephthalate Coatings as Affected by Mechanical Pretreatment of Powder in The Course of Preparation," *Mekhanika Kompozitnykh Materialov*, vol. 30, no. 4, pp. 455-463, 1994.
  - [88] M. L. Belonozhko, O. M. Barbakov, and A. L. Abramovsky, "Development of Tourism in The Arctic Zone and Its Impact on Environment," *Journal of Environmental Management and Tourism*, vol. 9, no. 8, pp. 1642-1650, 2018.
  - [89] E. L. Kuznetsova, G. V. Fedotenkov, and E. I. Starovoitov, "Methods of Diagnostic of Pipe Mechanical Damage Using Functional Analysis, Neural Networks and Method of Finite Elements," *INCAS Bulletin*, vol. 12, Special Issue, pp. 79-90, 2020.
  - [90] V. I. Gencheva, L. A. Omelyanchik, D. M. Fedoryak, A. A. Brazhko, and M. P. Zavgorodny, "Study of Biological Activity of Some 4-S-Derivatives of Quinoline," *Biopolymers and Cell*, vol. 22, no. 6, pp. 475-479, 2006.
  - [91] K. B. Biyashev, A. Z. Makbuz, and B. K. Biyashev, "Occurrence of Enteroinfectious Pathogens in Agricultural Animals and Poultry," *Biology and Medicine*, vol. 8, no. 2, article number BM-170-16, 2016.
  - [92] A. Z. Khastayeva, V. S. Zhamurova, L. A. Mamayeva, A. T. Kozhabergenov, N. Z. Karimov, and K. M. Muratbekova, "Qualitative Indicators of Milk of Simmental and Holstein Cows in Different Seasons of Lactation," *Veterinary World*, vol. 14, no. 4, pp. 956-963, 2021.
  - [93] S. S. H. Tashpulatov, I. V. Cherunova, E. G. Andreeva, B. G. Alimukhamedova, and G. A. Ganieva, "Research and Comprehensive Assessment of The Performance Properties of Thread Connections in The System Adras + Polymer Composite," *Izvestiya Vysshikh Uchebnykh Zavedenii, Seriya Tekhnologiya Tekstil'noi Promyshlennosti*, vol. 2018, no. 6, pp. 150-153, 2018.
  - [94] N. Fialko, R. Navrodska, M. Ulewicz, G. Gnedash, S. Alioshko, and S. Shevcuk, "Environmental Aspects of Heat Recovery Systems of Boiler Plants," *E3S Web of Conferences*, vol. 100, article number 00015, 2019.
  - [95] I. Cherunova, S. Tashpulatov, and S. Kolesnik, "Automation of Deformed Fibrous Materials Thermal Characteristics Accounting Process in Garments Production," *2018 International Russian Automation Conference, RusAutoCon*, vol. 2018, article number 8501795, 2018.
  - [96] N. M. Fialko, R. O. Navrodska, G. O. Gnedash, G. O. Presich, and S. I. Shevchuk, "Study of Heat-Recovery Systems of Or Heating and Moisturing Combustion Air of Boiler Units," *Science and Innovation*, vol. 16, no. 3, pp. 43-49, 2020.
  - [97] G. M. Hryhorenko, L. I. Adeeva, A. Y. Tunik, M. V. Karpets, V. N. Korzhyk, M. V. Kindrachuk, and O. V. Tisov, "Formation of Microstructure of Plasma-Arc Coatings Obtained Using Powder Wires with Steel Skin and B4C + (Cr, Fe)7C3 + Al Filler," *Metallofizika i Noveishie Tekhnologii*, vol. 42, no. 9, pp. 1265-1282, 2020.
-

- 
- [98] M. L. Belonozhko, L. N. Belonozhko, and S. S. Siteva, "Digital Tourism in The Development of The Arctic Region," *Journal of Environmental Management and Tourism*, vol. 9, no. 6, pp. 1154-1164, 2018.
  - [99] I. V. Muradov, E. Y. Sidorova, and L. N. Korshunova, "Improving the Classification of Integration Risks on Example of The Eurasian Economic Union," *International Multidisciplinary Scientific GeoConference Surveying Geology and Mining Ecology Management, SGEM*, vol. 5, pp. 293-300, 2020.
  - [100] L. I. Goncharenko, E. Y. Sidorova, A. A. Artemev, and N. A. Nazarova, "Dividend-Based and Interest-Based Schemes of Minimization of Customs Value of Goods in Deals Between Related Parties: Russian Practice," *Espacios*, vol. 39, no. 16, pp. 1-10, 2018.
  - [101] I. V. Cherunova, S. S. Tashpulatov, and S. V. Kurenova, "Treated Textile Electrostatic Properties Study," *Materials Science Forum*, vol. 992, pp. 439-444, 2020.
  - [102] V. Sydorets, V. Korzhyk, V. Khaskin, O. Babych, and O. Berdnikova, "On the Thermal and Electrical Characteristics of The Hybrid Plasma-MIG Welding Process," *Materials Science Forum*, vol. 906, pp. 63-71, 2017.
  - [103] N. M. Fialko, V. G. Prokopov, N. O. Meranova, Yu. S. Borisov, V. N. Korzhik, and G. P. Sherenkovskaya, "Heat Transport Processes in Coating-Substrate Systems Under Gas-Thermal Deposition," *Fizika i Khimiya Obrabotki Materialov*, vol. 2, pp. 68-75, 1994.
  - [104] G. A. Ganiyeva, B. R. Ryskulova, and S. S. Tashpulatov, "Selection of Special Clothes Design Parameters on the Basis of Optimisation of Dynamic Conformance Parameters," *International Journal of Applied Engineering Research*, vol. 10, no. 19, pp. 40603-40606, 2015.
  - [105] G. M. Grigorenko, L. I. Adeeva, A. Y. Tunik, V. N. Korzhik, and M. V. Karpets, "Plasma Arc Coatings Produced from Powder-Cored Wires with Steel Sheaths," *Powder Metallurgy and Metal Ceramics*, vol. 59, no. 5-6, pp. 318-329, 2020.
  - [106] V. A. Pogodin, A. N. Astapov, and L. N. Rabinskiy, "CCCM Specific Surface Estimation in Process of Low-Temperature Oxidation," *Periodico Tche Quimica*, vol. 17, no. 34, pp. 793-802, 2020.
  - [107] S. A. Montayev, B. T. Shakeshev, M. Z. Ryskaliyev, N. B. Adilova, and K. A. Narikov, "Collagen Agent Technology for Foam Concrete Production," *ARPJ Journal of Engineering and Applied Sciences*, vol. 12, no. 5, pp. 1674-1678, 2017.
  - [108] L. N. Nutfullaeva, A. F. Plekhanov, I. G. Shin, S. S. H. Tashpulatov, I. V. Cherunova, S. H. N. Nutfullaeva, and E. A. Bogomolov, "Research of Conditions of Formation Package and Ensure the Safety of the Pillows from Composite Nonwoven Fibers Materials," *Izvestiya Vysshikh Uchebnykh Zavedenii, Seriya Tekhnologiya Tekstil'noi Promyshlennosti*, vol. 380, no. 2, pp. 95-101, 2019.
  - [109] V. N. Korzhyk, L. D. Kulak, V. E. Shevchenko, V. V. Kvasnitskiy, N. N. Kuzmenko, X. Liu, Y. X. Cai, L. Wang, H. W. Xie, and L. M. Zou, "New Equipment for Production of Super Hard Spherical Tungsten Carbide and Other High-Melting Compounds Using the Method of Plasma Atomization of Rotating Billet," *Materials Science Forum*, vol. 898, pp. 1485-1497, 2017.
  - [110] X. Jiang, "Incorporating Service Design for Industry 4.0: A Scientometric Review for Green and Digital Transformation Driven by Service Design," *Management Science Informatization and Economic Innovation Development Conference, MSIEID 2020*, vol. 9382585, pp. 296-299, 2020.
  - [111] R. Dinzhos, N. Fialko, V. Prokopov, Y. Sherenkovskiy, N. Meranova, N. Koseva, V. Korzhik, O. Parkhomenko, and N. Zhuravskaya, "Identifying the Influence of The Polymer Matrix Type on The Structure Formation of Microcomposites When They Are Filled with Copper Particles," *Eastern-European Journal of Enterprise Technologies*, vol. 5, no. 6-107, pp. 49-57, 2020.
  - [112] Y. Borisov, V. Korzhyk, and S. Revo, "Electric and Magnetic Properties of Thermal Spray Coatings with an Amorphous Structure," *Proceedings of the International Thermal Spray Conference*, vol. 1, pp. 687-691, 1998.
-

- 
- [113] S. Peleshenko, V. Korzhyk, O. Voitenko, V. Khaskin, and V. Tkachuk, "Analysis of The Current State of Additive Welding Technologies for Manufacturing Volume Metallic Products (Review)," *Eastern-European Journal of Enterprise Technologies*, vol. 3, no. 1-87, pp. 42-52, 2017.
  - [114] G. A. Ganiyeva, B. R. Ryskulova, and S. Sh. Tashpulatov, "Ergonomic Studies of Dynamic Compliance of Parameters Within the Man-Special Clothing System for Workers of The Oil Industry," *Izvestiya Vysshikh Uchebnykh Zavedenii, Seriya Tekhnologiya Tekstil'noi Promyshlennosti*, vol. 2015, no. 3, pp. 151-154, 2015.
  - [115] Y. Sun, M.Y. Kuprikov, E.L. Kuznetsova, "Effect of Flight Range on The Dimension of The Main Aircraft," *INCAS Bulletin*, vol. 12, Special Issue, pp. 201-209, 2020.
  - [116] K. Temur, and S. T. Imeci, "Tri Resonance Multi Slot Patch Antenna," *Heritage and Sustainable Development*, vol. 2, no. 1, pp. 30-37, 2020.
  - [117] G. M. Grigorenko, L. I. Adeeva, A. Y. Tunik, V. N. Korzhik, L. K. Doroshenko, Y. P. Titkov, and A. A. Chaika, "Structurization of Coatings in The Plasma Arc Spraying Process Using  $B_4C + (Cr, Fe)_7C_3$ -Cored Wires," *Powder Metallurgy and Metal Ceramics*, vol. 58, no. 5-6, pp. 312-322, 2019.
  - [118] I. Cherunova, S. Tashpulatov, and Y. Davydova, "Geometric Conditions of Mathematical Modeling of Human Heat Exchange Processes with The Environment for CAD Systems Creating Heat-Shielding Clothing," *IOP Conference Series: Materials Science and Engineering*, vol. 680, no. 1, article number 012039, 2019.
  - [119] Y. Li, A. M. Arutiunian, E. L. Kuznetsova, and G. V. Fedotkov, "Method for Solving Plane Unsteady Contact Problems for Rigid Stamp and Elastic Half-Space with A Cavity of Arbitrary Geometry and Location," *INCAS Bulletin*, vol. 12, Special Issue, pp. 99-113, 2020.
  - [120] S. S. Tashpulatov, I. and V. Cherunova, M. and K. Rasulova, D. and D. Inogamdjanov, M. and Yu. Umarova, A. and D. Daminov, U. and R. Uzakova, S. and G. Jurayeva, "Development of The Calculation Method of Polymer Compound Mass to Be Applied onto The Textile Garment Pieces," *IOP Conference Series: Materials Science and Engineering*, vol. 459, no. 1, article number 012067, 2018.
  - [121] N. M. Fialko, R. O. Navrodska, S. I. Shevchuk, and G. O. Gnedash, "The Environmental Reliability of Gas-Fired Boiler Units by App Lying Modern Heat-Recovery Technologies," *Naukovyi Visnyk Natsionalnoho Hirnychoho Universytetu*, vol. 2020, no. 2, pp. 96-100, 2020.
  - [122] M. M. Lazarenko, K. I. Hnatiuk, S. A. Alekseev, K. S. Yablochkova, R. V. Dinzhos, F. Ublekov, M. V. Lazarenko, D. A. Andrusenko, and A. N. Alekseev, "Low-Temperature Dielectric Relaxation in the System Silica Gel – Undecylenic Acid," in: *Proceedings of the 2020 IEEE 10th International Conference on "Nanomaterials: Applications and Properties", NAP 2020*, Sumy, Ukraine, article number 9309579, pp. 9-13, 2020.
  - [123] V. P. Privalko, R. V. Dinzhos, and E. G. Privalko, "Melting Behavior of the Nonisothermally Crystallized Polypropylene/Organosilica Nanocomposite," *Journal of Macromolecular Science – Physics*, vol. 43B, no. 5, pp. 979-988, 2004.
  - [124] H. K. Silman, and A. E. Ali, "Breast Cancer Identification Based on Artificial Intelligent System," *Sustainable Engineering and Innovation*, vol. 2, no. 2, pp. 41-49, 2020.
-